



Geotechnical viability of sand, cement, and binary stabilisation of superficial soils in the western Niger Delta: an example of Warri City, Southern Nigeria

Enivwenaye Oghenero Avwenagha^{1,*} , Jerry Osokpor² , Brume Overare^{2,3} , Ovie Benjamin Ogbe² , Samuel Okon Essang⁴ , Ogie Macaulay Ekhalialu¹ , Godwin Okumagbe Aigbadon⁵ 

¹Department of Earth Sciences, Arthur Jarvis University, P.M.B. 1404, Calabar, Nigeria.

²Department of Geology, Federal University of Petroleum Resources, Effurun, Nigeria.

³Department of Earth Sciences, Memorial University of Newfoundland, St. John's, NL, A1B 3X5, Canada.

⁴Department of Mathematics and Computer Science, Arthur Jarvis University, Calabar, Nigeria.

⁵Department of Geology, University of Benin, Benin City, Edo State, Nigeria.

Abstract

The pavement performance of superficial soils in southern Nigeria is in decline, most notably due to the use of inferior pavement materials and poor soil conditions. The study, therefore, examines the impact of sand, cement, and binary (sand/cement) stabilisation on soils in an attempt to improve road development in the City of Warri. The natural condition of sixteen (16) soil samples was subjected to consistency tests, classification tests, compaction, and soaked California Bearing Ratio (CBR) analyses as a standard for comparative analysis. The effects of sand, cement, and binary stabilisation on the engineering behaviour and suitability of natural soils were examined using specified road standards, CBR responses, and t-test analysis as bases for comparison with the natural, untreated soils. The properties of natural and treated soils were fed into machine learning predictive model, including Random Forest Model (RFM), Extreme Gradient Boosting (XGBoost) Model, and Explainable Boosting Model (EBM), for CBR prediction evaluation. Results confirmed that sand stabilisation had a significant impact on the soil grade, with a marginal impact on the natural CBR (resulting in a slight boost from the natural range of 3-17.9% to 11-28.8%), while the soil suitability remained constant. Cement-treated soils were improved to subbase/base quality (71.3-193.3%) at 7 wt. % cement. Binary stabilisation resulted in base-quality soils (107-272.5%). T-test analyses confirmed that binary stabilisation is the most technically viable solution to the pavement deficiency in the City. The study presents a feasibility resource database for the stabilisation of deficient superficial soils for road development in deltaic environments.

Article Information

Publication type: Research Papers
Received 31 October 2025
Accepted 5 January 2026
Online pub. 12 January 2026
Editor: Evandro Klein

Keywords:
Compaction
California Bearing Ratio
t-test analysis
Machine
Model

*Corresponding author
Enivwenaye Oghenero Avwenagha
E-mail address: enivwe@gmail.com
avwenagha.oghenero@arthurjarvisuniversity.edu.ng

1. Introduction

The superficial soils in the western Niger Delta are mainly residual lateritic soils in nature (Avwenagha et al. 2014b; Avwenagha et al. 2024; Eze-Uzomaka and Omotosho 2008). They are the most widely used material for road pavement design (Arumala and Akpokodje 1987), notwithstanding their exposures to aggressive rainfall of about 3000mm (Adejuwon 2012), high temperature conditions, and problematic geotechnical soil conditions, which limit their engineering competence. In addition, there is widespread urbanisation, which adversely impacts the superficial soils of the Western Niger Delta (specifically in the City of Warri).

Warri is one of the fastest-growing metropolitan cities in the Western Niger Delta with evidence of rapid population growth

(Mogborukor et al. 2021; Sajini 2021), widespread installation of medium-heavy residential/ industrial infrastructures (buildings, oil and Gas installations) and heavy vehicular traffic (Ugbe 2011; Avwenagha et al. 2014b). These developmental pressures not only stress/ burden the foundation soils but trigger unguided installation of earthworks on problematic soils, which are typical of the Niger Delta and beyond (Okagbue 1989; Puppala et al. 2015; Nwankwoala 2021, 2023; Ugbe 2022). The weak soil conditions, such as high moisture content, high fine content, swelling clays, and lateral soil variation, have resulted in differential settlement, swells, cracks, potholes, and erosion of road pavement as reported by other workers (Akpokodje et al. 1987b; Ugbe et al. 2022). These defects have translated to a high cost of road maintenance and haulage of fill materials for soil replacement (Jain et al. 2020).

Moreover, it has been noticed that the superficial soils in the western Niger Delta do not exceed a CBR (California Bearing Ratio) of 30% under natural or untreated conditions (Avwenagha et al. 2014b, 2024). This means that the soils cannot function as subbase and base courses under heavy vehicular loads, which are peculiar to the City. Hence, a technical and economic solution to these road failures is soil stabilisation. Soil stabilisation is the regulated addition of geo-material (stabilisers) to incompetent soils to enhance their engineering performance and suitability for earthwork constructions. The objectives of soil stabilisation are to reduce permeability, prevent swelling (Puppala et al. 2015), and improve soil consistency/ strength (Amu and Adetuberu 2010). There are different stabilisation schemes, but the choice of stabilisation depends on the eco-friendliness (Goodarzi et al. 2015; Latifi et al. 2015; Sathyapriya and Arumairaj 2016; Latifi et al. 2016; Puppala et al. 2015), geotechnical/ economic viability of the stabilizer, and the uniqueness of the scheme (Avwenagha et al. 2024). Several researchers have attempted soil stabilisation in the Niger Delta (Omotosho and Eze-Uzomaka 2008; Okagbue and Onyeobi 1999; Akpokodje et al. 1987a; Imafidon et al. 2021; Avwenagha et al. 2024). Omotosho and Eze-Uzomaka (2008) engaged sand, cement, and binary (Mixed sand-cement) stabilisation in the Eastern Niger Delta and produced a subgrade, subbase, and base-quality soil material, respectively. They also established that it is technically and economically unviable for cement stabilisation of deltaic laterites to yield a base course-quality soil at 7 wt% of cement content. Okagbue and Onyeobi (1999) conducted marble dust stabilisation and noticed that deltaic laterites can produce a CBR of 26% at best using 6-8% marble dust. Imafidon et al. (2021) carried out sand and composite stabilisation of superficial soils in parts of the western Niger Delta and established that the latter stabilisation is more viable from the economic and technical perspectives. Avwenagha et al. (2024) attempted a stone-dust stabilisation of superficial soils in the western Niger Delta and produced subbase-quality

soils at 30% stone dust. They (Avwenagha et al. 2024) also reported that stone dust significantly impacts the grading of soils, but marginally affects the quality of soil cohesion/ inter-particle bonding. A similar stabilisation was conducted on the superficial soils of India (Mishra et al. 2019), and they reported a subgrade and subbase category of soils based on the Indian road specification standard (MoRTH 2013), which agrees with the Nigerian Road specification scheme (Nigeria 1997).

Based on the overwhelming dominance of sand over fines (Olurunfemi 1984) and the zero-low cohesion in superficial soils of the Western Niger Delta, the use of cement stabilisation and mixed stabilisation (sand+cement) promises to be viable (Puppala et al. 2015; Pillappa 2005). Hence, the focus of the study is to assess the technical and economic viability of cement, sand, and Binary stabilisation as a solution to incessant road failure and road development in the deltaic environment.

The study seeks to:

- Assess the geotechnical impact of sand, cement, and Binary (sand/cement) stabilisation schemes on the road performance of the soils.
- Examine the impact of the sand stabilisation on the compaction and A.A.S.H.T.O. classification signatures of the superficial soils.
- Compare the geotechnical viability of each stabilisation scheme using a t-test analysis.
- Adopt a more reliable predictive model for the CBR performance of stabilised soils.

The area is located in the western portion and coastal zone of the Nigerian Niger Delta, some 40 kilometres away from the shores of the Atlantic Ocean. The area is a prominent centre of commercial activities in southern Nigeria, which lies between longitudes 5°25'E-5°49'E and latitudes 5°33'N-5°37'N. It occupies a flat, low-lying terrain which is drained and moderately dissected by the River Warri and its network of tributaries, which empty into the sea (Figure 1). The flat terrain is evidenced by a dendritic drainage pattern, which also indicates a homogeneous underlying soil material.

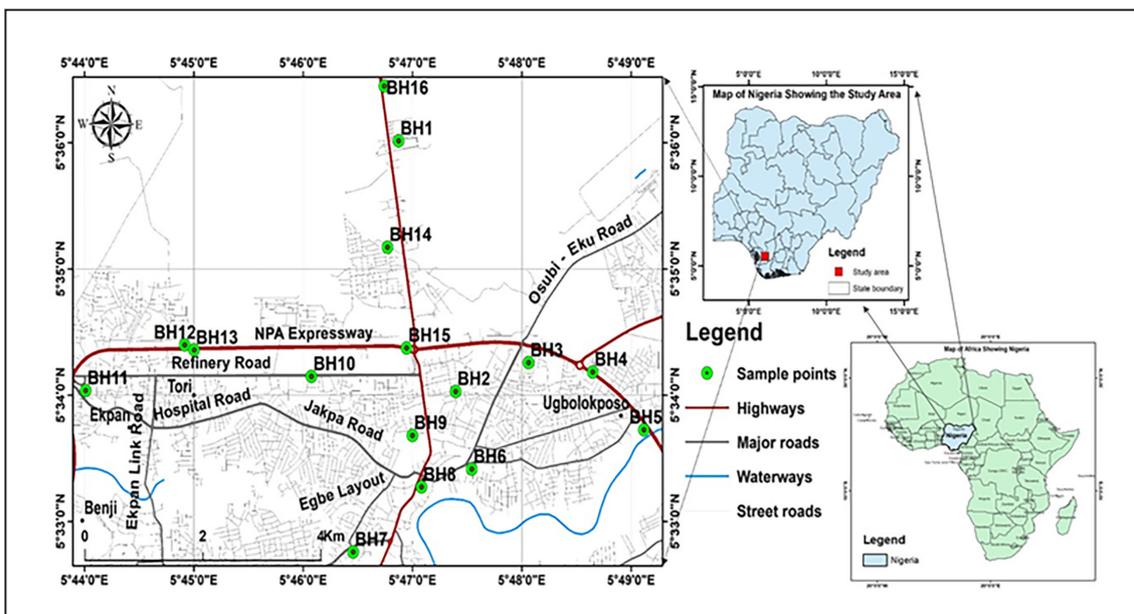


Figure 1: Location and geographical map of Warri (study area).

the Niger Delta region, especially in areas north of Warri, where it is shallow. The thickness of the Formation is variable but generally exceeds 2000meters. Detailed studies of the Quaternary deposits overlying the Benin Formation revealed that the sediments were deposited under the influence of fluctuating Pleistocene eustatic sea levels. These sediments vary greatly in type.

The Agbada Formation consists of a sequence of alternating deltaic sands and shales. It is Eocene to Oligocene in age and exceeds 3000meters in thickness. This Formation is the oil reservoir of the Niger Delta Basin. It is rich in microfauna at the base, decreasing upward, and thus indicating an increasing rate of deposition in the Delta front. A fluvial origin is indicated by the coarsening of the grains and poor sorting. The formation underlies the entire Delta area and may be continuous with the Ogwashi-Asaba and Ameki Formation.

The Akata Formation rests unconformably on the migmatite-gneiss basement complex and forms the basal unit of the Niger Delta stratigraphic pile. This Formation consists of an open marine facies unit dominated by high-pressure carbonaceous shales. The formation ranges in age from Palaeocene to Eocene, and its thickness could exceed 1000 meters.

3. Materials and methods

Field investigations were undertaken by engaging geotechnical surveys such as hand auger drilling programmes and soil samplings. Sixteen boreholes were drilled to a depth of 4m, and samples were collected at intervals of 0.75 meter

for laboratory examinations based on BS 5930 (BSI 2015). The GPS coordinates of sampled locations were recorded (Table 1).

In compliance with standard test procedures BS 5930 (BSI 2015) and BS 1377-9 (BSI 2022), samples recovered from auger holes were subjected to the following testing programmes: sieve analysis, consistency limit tests (such as liquid limit, plastic limit), compaction, and California Bearing Ratio (CBR) analysis (Figure 3). Two types of sieve analyses were engaged in assessing the particle size distribution (PSD) of recovered soil samples, which are dry and wet sieve analyses according to BS 1377-2 (BSI 2022). For dry sieve analysis, 200g of oven-dried soil sample was pulverised to separate the individual grain sizes and passed through a set of sieves arranged from top to bottom in a decreasing order of mesh/ sieve sizes as shown in the sequence: 4.75mm, 2.36mm, 0.84mm, 0.42mm, 0.149mm, and 0.074mm. The sample within the set of sieves was agitated by an electric shaker for 15 minutes. A weight of the sample retained in the individual sieves was recorded, and the percentage by mass of sample passing through each sieve was calculated and plotted against the respective sieve sizes to produce a Particle Size Distribution (PSD) curve from which the PSD of the sample was determined. A wet sieve analysis is conducted when the fine content in a sample is more than 5% based on BS 1377-2 (BSI 2022). By visual examination, some soil samples satisfied this condition, hence the analysis. Soil material of 200g was dried and washed through a sieve No.200 (0.074mm) to separate the fines from the coarse fractions. The coarse fraction was dried and subjected to mechanical sieving using dry sieve analysis (which had earlier been explained).

Table 1: Coordinates of the sample locations in Warri.

S/N	Sample location	Coordinates
1	BH1(Mercy City)	N05°36'00.81", E005°46'52.5"
2	BH2 (Effurun GRA)	N05°34'01.8" E005°47'23.8"
3	BH3 (PTI Junc.)	N05°34'15.4" E005°48'03.8"
4	BH4 (Ebrumede)	N05°34'11.0" E005°48'39.0"
5	BH5 (Ugbomoro)	N05°33'43.5" E005°49'07.1"
6	BH6(Alegbo)	N05°33'24.9" E005°47'32.6"
7	BH7 (Sokoh Estate)	N05°32'45.5" E005°46'27.5"
8	BH8 (Airport Junction)	N05°33'16.3" E00°047'05.0"
9	BH9 (Okoloba Junction)	N05°33'40.8" E005°47'00.0"
10	BH10 (Mekavaal Hotel)	N05°34'08.9" E005°46'04.6"
11	BH11 (Ekpan Fly-Over)	N05°34'02.2" E005°44' 00.6"
12	BH12 (Niger Cat)	N05°34'23.8" E005°44' 55.0"
13	BH13 (Burrow Pit)	N05°34'21.4" E005°45' 00.2"
14	BH14 (Army Estate)	N05°35'10.3" E005°46' 46.4"
15	BH15 (Shoprite)	N05°34'22.4" E005°46' 56.8"
16	BH16 (Kola Garden Hotel)	N05°36'26.9" E005°46' 44.6"

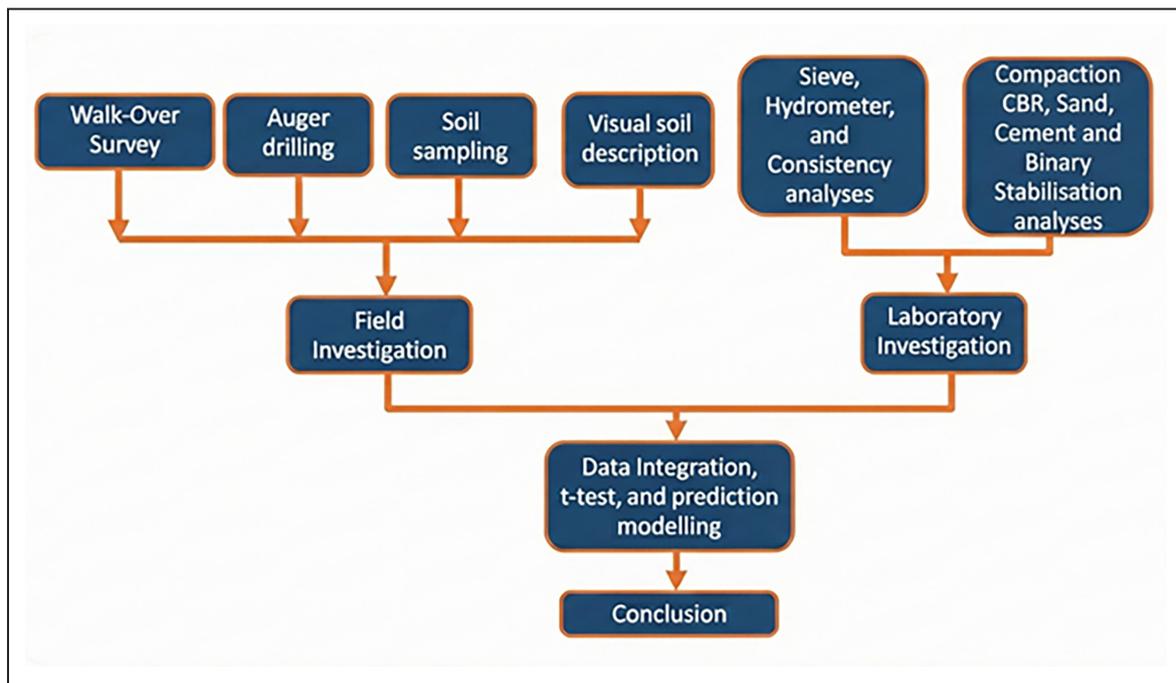


Figure 3: Flow chart of the study methods.

The liquid limit was determined using the Casagrande method (Casagrande 1948). Initially, the soil samples were air-dried, disaggregated, and passed through a sieve diameter of 0.425mm and thoroughly mixed with a small amount of distilled water until it appeared as a smooth, uniform paste according to BS 1377-2 (BSI 2022). A portion of the paste was placed into the cup of the liquid limit apparatus, and then squeezed down to eliminate air pockets and spread into the cup to a depth of about 10mm, thereby forming an approximately horizontal surface. The groove tool was carefully used to cut a clean, straight groove down the centre of the cup, then the crank of the apparatus was turned at a rate of approximately two drops per second, and the number of drops, "N," was counted. When the number of drops exceeded 50, the number of drops on the data sheet was recorded, and then soil samples from the apparatus cup, usually from both ends of the groove, were taken using a spatula. The soil was placed into a moisture can where it was immediately weighed, covered, and placed in an oven for about 16 hours. The soil remaining in the apparatus cup was later placed into the porcelain dish as the apparatus cup was cleaned and dried for a second and third round of analysis, which was done by gradually increasing the moisture content of the paste to achieve groove closure at lesser blows. Finally, a graph of moisture content was plotted against the number of blows. The moisture content at the 25th blow gave the liquid limit.

A 20g dry soil sample was used for the plastic limit test. This was mixed with distilled water to form a uniform paste until the soil was at a consistency where it could be rolled without sticking to the hands. By rolling between the palm and the glass plate, an ellipsoidal mass was formed. The mass with cracks was rolled until it formed a thread of 3mm in diameter, having cracks on its surface. The thread was broken into several pieces and placed into a moisture can and sealed. The Can was then oven-dried for 16 hours, and finally, the moisture content of the set of threads was determined.

The whole procedure was repeated three times to obtain three determinations. The average value of the moisture content gave the plastic limit of the soil.

For the sand stabilisation test, Coastal Plain Sands (also known as sharp sand, which had less than 5% fines) were sourced from River Ologbo in the Western Niger Delta. A regulated proportion of the sands in the range of 30-55 wt.% (depending on the soil grade of the sample) was thoroughly mixed with 3kg of the soil samples from sixteen locations of the study area, and each was subjected to the standard proctor compaction test in compliance with BS 1377-4 (BSI 2022). OMC and MDD values of each sample were used to prepare a 6kg compacted specimen for CBR analysis, which was conducted after being wax-cured for 6days and soaked for 24hours in water as prescribed by Nigeria (1997).

For the cement stabilisation test, 3kg of soil specimens from all the study locations were mixed with ordinary Portland cement in conformity with BS 12 (BSI 1990). Regulated proportions of cement in the range of 7-11wt% were added depending on the soil's AASHTO classification, as in Table 2. Cement-mixed specimens were subjected to the standard proctor compaction test from which the OMC and MDD were used to produce a 6000 g cement-stabilised specimen for CBR analysis after the specimen was wax-cured for six days, soaked in water for 24 hours, and allowed to drain for 15 minutes.

The Binary (Sand + Cement) Stabilisation test was engaged in order to enhance the technical and economic viability of soil stabilisation, bearing in mind the costly nature of cement. In this case, 3kg of 16 soil samples were thoroughly mixed with sharp sands in the range of 30-55 wt.% to improve their AASHTO soil group. Following the upgrade, a uniform cement proportion of 7wt% was mixed with the soil specimen in compliance with the provisions of BS 1924 (BSI 1990). Thereafter, a 3000g specimen mixed with sand and cement was subjected to the standard proctor compaction test from

Table 2: Modified Cement Content Requirements of AASHTO. Soil Groups.

S/N	A.A.S.H.T.O Soil Group	Range of Cement content (wt%)
1	A-1-a	4-6
2	A-1-b	4-7
3	A-2	5-8
4	A-3	6-9
5	A-4	7-11
6	A-5	8-12
7	A-6	9-13
8	A-7	10-14

Source: BS6229 (1990)

which the OMC and MDD were used to prepare a specimen for CBR analysis after the sample was wax-cured for 6days, soaked in water for 24 hours, and allowed to drain for 15minutes in agreement with BS 1924 (BSI 1990) and Nigeria (1997).

For reasons of management of time and stress in conducting a series of analyses for an adequate quantity of stabilisers and quality CBR performance, three predictive models (Random Forest, Extreme Gradient Boosting, and Enabling Boosting Machine models) were employed. Each model was trained on a unified dataset encompassing soil physical features, including sand and cement content, fine percentage, plasticity characteristics, optimal moisture content (OMC), and maximum dry density (MDD). An interaction term (Sand × Cement) was incorporated to elucidate the synergistic effects between stabilising agents. The dataset was divided into an 80/20 training-testing ratio. R^2 (coefficient of determination) was employed to assess goodness-of-fit, whilst MSE (mean squared error) quantified the average prediction error. Cross-validation was employed to ensure performance reliability, and feature importance was assessed for each model to identify the input variables that most significantly influenced CBR prediction.

4. Results

4.1 Natural Soil Condition

The Table 3 shows the compaction and geotechnical properties of the superficial soils in their natural state. The sand content ranges from 3.5-87.2% with an average value of 73.13%. The highest sand content was recorded in BH11, while the least sand content was noticed in BH1. The dominance of sand over fines was noticed in all boreholes except BH1, which has 3.5% and 96.5% sand and fines, respectively.

4.1.1 Liquid limit

The liquid limits ranged from 14.5%-69.0% with an average of 28.2%. The highest liquid limit was noticed in BH1, while the least in BH11 (Table 3). The liquid limits of the soils are generally low (<35%) except for BH1 with a value of 69%. A similar trend applies to the Plasticity index (PI), which ranged from 11.08-22.0% with generally low PI of less than 12% except BH1 with a value of 22%.

4.1.2 Optimum Moisture Content (OMC) and Maximum Dry Density (MDD)

The Optimum Moisture Content (OMC) ranged from 8.41-23.0% and averages 9.91%, which implies a general dominance of low OMC except for BH1 (Table 3). The Maximum Dry Density (MDD) ranged from 1.395-1.944g/cm³. In this case, there is generally high MDD (with an average of 1.8696 g/cm³). The variation trend in OMC and MDD translated into California Bearing Ratio (CBR), which ranged from 3-17.90%. (Figure 4). The average CBR value (14.3%) implies a dominantly low CBR on the scale of road performance standards (Nigeria 1997). Hence, soil stabilisation is needed.

4.1.3 Influence of sand, cement, and binary (sand+cement) stabilisation on natural soils

In response to sand stabilisation at 30% sand addition, there was a general decline in the natural soil consistency limits and OMC (Tables 3 and 4). The average fines, liquid limit, plastic limit, plasticity indices of the natural superficial soils declined from 30.4 -21.5%, 28.2-19.97%, 19.06-15.08%, 9.91-5.68%, and 11.45-10.75% respectively (Tables 3 and 4). These declines translated into an overall increase in average MDD (from 1.8696 to 1.9426 g/cm³) and average CBR (from 14.3 to 22.865%). This implies that by the effect of sand stabilisation, there is an average increase in soil CBR and MDD by 30% and 3.9% respectively.

The trend of variation between consistency limits and compaction characteristics of soil (OMC and MDD) in sand stabilisation is similar to those of cement and binary (sand/cement) stabilisation (Table 5), but their impacts on natural soil CBR differ (Figure 5A-C). The Cement stabilisation of samples from BH 2-16 and BH 1 was conducted using 7-10 wt. % and 11% cement, respectively (BS12-1990, Table 6). In response to cement stabilisation using 7-10wt% cement (for BH2-16) and 11wt% (for BH1 only), the average natural MDD and CBR increased from 1.8696-1.9193g/cm³ and 14.3-166.94%. By effect of binary stabilisation (30wt% sand+7wt% cement) on the natural soils, the natural CBR increased by 110-272.5% with an average increase by 212% (for BH 2-16, Figure 5) while that of BH1 increased by 130% (at 55wt% sand and 7wt% cement). The CBR values of all soil samples increased progressively with response to cement, sand, and binary stabilisation (Figure 5A-C).

Table 3: Compaction and geotechnical properties of the superficial soils in their natural state.

Borehole-Number	Depth (m)	% Sand	% Fine	Liquid Limit	Plastic Limit	Plasticity Index	USCS	AASHTO	OMC %	MDD g/cm ³	CBR %
BH1	0-4	3.50	96.50	69.00	47.00	22.00	MH	A7-5	23	1.395	3.00
BH2	0-4	78.00	22.00	18.40	11.90	6.50	CL	A2-4	10.43	1.901	16.20
BH3	0-4	65.50	34.50	31.10	18.70	12.40	CL	A2-6	9.72	1.944	11.90
BH4	0-4	60.40	39.60	33.00	20.60	12.40	CL	A-6	9.80	1.925	10.10
BH5	0-4	78.20	20.80	25.40	17.70	7.70	CL	A2-4	11.82	1.901	15.90
BH6	0-4	72.20	27.80	25.70	15.20	10.50	CL	A2-4	11.78	1.892	15.00
BH7	0-4	74.30	25.70	22.50	18.40	4.10	CL	A2-4	9.10	1.927	15.50
BH8	0-4	79.20	20.80	25.40	15.60	9.80	CL	A2-4	9.42	1.886	17.90
BH9	0-4	82.30	17.70	19.80	14.40	5.40	CL	A2-4	9.87	1.925	17.80
BH10	0-4	75.20	24.80	26.10	18.80	7.30	CL	A2-4	8.41	1.904	17.30
BH11	0-4	87.20	12.80	14.50	NP	NP	CL	A-3	12.64	1.906	16.20
BH12	0-4	76.80	23.20	22.50	18.00	4.50	CL	A2-4	12.20	1.856	15.80
BH13	0-4	81.50	18.50	21.00	18.50	11.80	CL	A2-4	12.13	1.881	17.30
BH14	0-4	70.20	29.80	33.00	20.60	12.40	CL	A2-6	9.61	1.944	14.10
BH15	0-4	60.10	39.90	35.40	21.40	13.60	CL	A-6	12.30	1.826	10.60
BH16	0-4	67.50	32.50	28.80	16.60	12.20	CL	A2-6	10.98	1.902	13.70

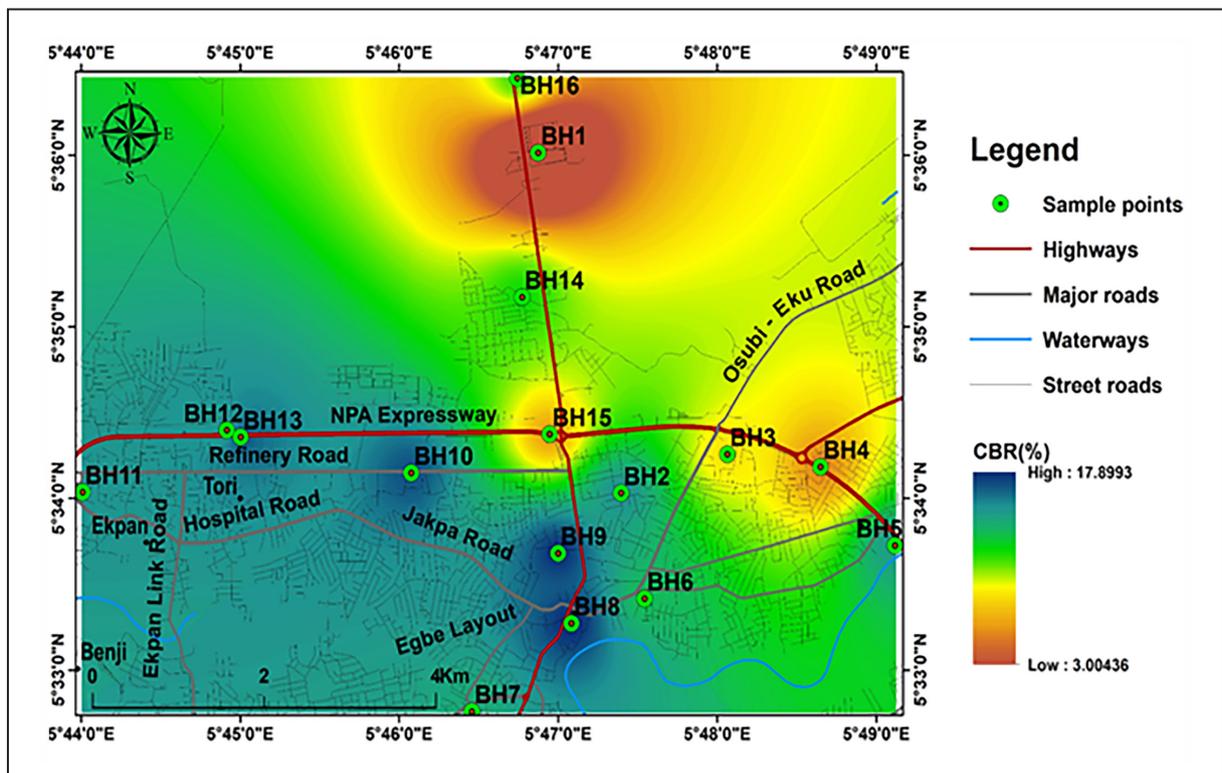


Figure 4: Natural CBR distribution of superficial soils in Warri. Note that the natural CBR distribution of the entire city does not exceed 18% which confirms that the untreated CBR of the soils is generally low and limited to subgrade quality (Nigeria 1997; Avwenagha et al. 2024). Moreover, on the CBR scale of 3-18%, over 80% of the City is marked by relatively medium-high CBR (as indicated by the green blue zone covering BH2-12), while about 20% of the area is marked by pockets of low-medium CBR (which is indicated by the orange-yellow/green zone; BH1, BH13-16).

Table 4: Results of sand stabilisation of the superficial soils.

Borehole Number	Depth (m)	modifying sand (wt%)	% Fine	Liquid Limit (%)	Plastic Limit (%)	Plasticity Index (%)	OMC (%)	MDD (g/cm ³)	USCS	AASHTO	CBR (%)
BH1	0-4	30.00	35.50	30.00	21.50	8.50	14.88	1.810	CL	A2-6	11.00
BH2	0-4	30.00	18.00	15.10	10.70	4.40	9.46	1.989	CL	A2-4	28.80
BH3	0-4	30.00	27.90	27.10	19.50	7.60	11.51	1.905	CL	A2-4	19.10
BH4	0-4	30.00	33.10	27.10	18.80	8.30	11.80	1.889	CL	A2-4	18.70
BH5	0-4	30.00	17.10	23.00	17.40	5.60	11.35	1.889	CL	A2-4	18.70
BH6	0-4	30.00	22.20	21.30	14.00	7.30	11.95	1.948	CL	A2-4	24.10
BH7	0-4	30.00	20.20	19.00	17.00	2.00	12.32	1.961	CL	A2-4	26.70
BH8	0-4	30.00	15.10	23.00	16.80	6.20	8.52	1.962	CL	A2-4	27.50
BH9	0-4	30.00	12.50	15.20	11.90	3.30	9.20	1.979	CL	A2-4	25.70
BH10	0-4	30.00	20.60	21.50	16.70	4.80	9.07	1.988	CL	A2-4	26.20
BH11	0-4	30.00	11.60	14.50	-	-	10.34	1.966	CL	A-3	26.70
BH12	0-4	30.00	16.20	15.50	12.90	2.60	10.36	1.961	CL	A2-4	26.20
BH13	0-4	30.00	14.20	18.70	15.70	3.00	9.53	1.990	CL	A2-4	28.60
BH14	0-4	30.00	23.20	28.30	18.30	10.00	9.20	1.972	CL	A2-4	20.40
BH15	0-4	30.00	30.80	25.10	15.90	9.20	11.91	1.921	CL	A2-4	17.00
BH16	0-4	30.00	25.30	22.30	14.30	8.00	10.60	1.952	CL	A2-6	20.40

Table 5: Results of cement stabilisation of the superficial soils.

Borehole Number	Depth (m)	modifying sand (wt%)	% Fine	Liquid Limit (%)	Plastic Limit (%)	Plasticity Index (%)	OMC (%)	MDD (g/cm ³)	USCS	AASHTO	CBR (%)
BH1	0-4	11.00	35.50	69.00	47.00	22.00	12.72	1.622	MH	A7-5	71.3
BH2	0-4	7.00	22.00	18.40	11.90	6.50	9.30	1.979	CL	A2-4	171.7
BH3	0-4	7.00	34.50	31.10	18.70	12.40	10.99	1.921	CL	A2-6	193.3
BH4	0-4	10.00	39.60	33.00	20.60	12.40	11.74	1.882	CL	A-6	128.5
BH5	0-4	7.00	20.80	25.40	17.70	7.70	11.25	1.935	CL	A2-4	170.0
BH6	0-4	7.00	27.80	25.70	15.20	10.50	11.84	1.920	CL	A2-4	168.7
BH7	0-4	7.00	25.70	22.50	18.40	4.10	11.21	1.941	CL	A2-4	163.4
BH8	0-4	7.00	20.80	25.40	15.60	9.80	8.46	1.939	CL	A2-4	168.0
BH9	0-4	7.00	17.70	19.80	14.40	5.40	9.12	1.964	CL	A2-4	189.2
BH10	0-4	7.00	24.80	26.10	18.80	7.30	8.95	1.965	CL	A2-4	175.6
BH11	0-4	7.00	12.80	14.50	-	-	10.29	1.964	CL	A-3	130.0
BH12	0-4	7.00	23.20	22.50	18.00	4.50	10.22	1.941	CL	A2-4	150.3
BH13	0-4	7.00	18.50	21.00	11.80	9.20	9.48	1.983	CL	A2-4	143.3
BH14	0-4	7.00	29.80	33.00	20.60	12.40	9.12	1.917	CL	A2-6	178.9
BH15	0-4	10.00	39.90	35.00	21.40	13.60	11.82	1.901	CL	A-6	133.6
BH16	0-4	7.00	32.50	28.80	16.60	12.20	10.55	1.934	CL	A2-6	185.0

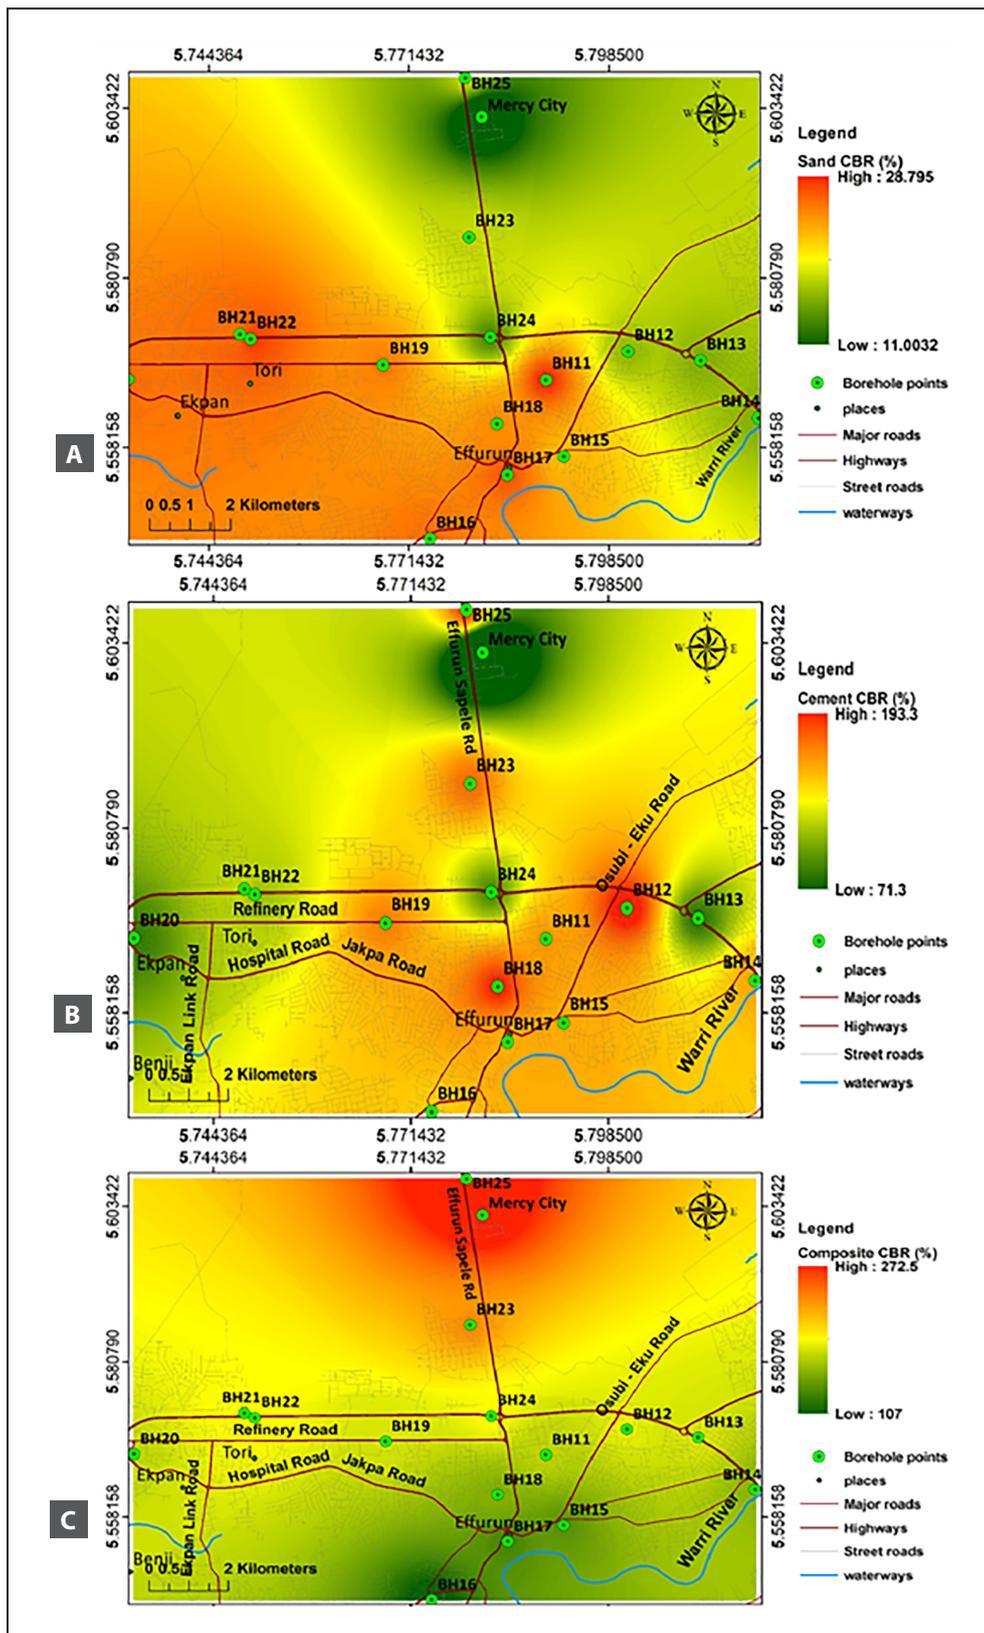


Figure 5: CBR trend maps of superficial soils in Warri, under conditions of sand, cement, and binary stabilisation, respectively. The green, yellow, and orange zones are lower, middle, and upper CBR levels in the CBR scale of the respective stabilisation schemes. Under natural/plain conditions of stabilisation (Figure 3), the CBR of the soils ranged from 3-18%. (A) Sand stabilisation - the CBR ranged from 11-28% which indicates improved subgrade-quality. (B) The CBR scale improved to a range of 71.3-193.3%, which falls within the class of subbase to base-quality soils. (C) Composite /Binary stabilisation - the distribution ranged from 107-272.5%, which depicts soil improvement to a class of slightly subbase to dominantly base-quality soils (Nigeria, 1997).

Table 6: Results of binary (sand+cement) stabilisation of the superficial soils.

Borehole Number	Depth (m)	Modifying-Sand (%)	Cement (wt%)	Liquid Limit (%)	Plastic Limit (%)	Plasticity Index (%)	OMC (%)	MDD (g/cm ³)	USCS	AASHTO	CBR (%)
BH1	0-4	55	7	30.00	21.50	8.50	14.67	1.771	CL	A2-6	130.7
BH 2	0-4	30	7	15.10	10.70	4.40	9.52	1.997	CL	A2-4	227.00
BH 3	0-4	30	7	27.10	19.50	7.60	10.99	1.921	CL	A2-6	207.40
BH 4	0-4	30	10	27.10	18.80	8.30	11.62	1.894	CL	A-6	221.70
BH 5	0-4	30	7	23.00	17.40	5.60	11.43	1.943	CL	A2-4	214.60
BH 6	0-4	30	7	21.30	14.00	7.30	12.12	1.953	CL	A2-4	229.90
BH 7	0-4	30	7	19.00	17.00	2.00	11.61	1.975	CL	A2-4	198.80
BH8	0-4	30	7	23.00	16.80	6.20	8.20	1.970	CL	A2-4	215.20
BH9	0-4	30	7	15.20	11.90	3.30	8.32	1.996	CL	A2-4	215.10
BH10	0-4	30	7	21.50	16.70	4.80	9.12	1.995	CL	A2-4	272.50
BH11	0-4	30	7	14.50	-	-	9.48	1.964	CL	A-3	107.00
BH12	0-4	30	7	15.50	12.90	2.60	10.45	1.968	CL	A2-4	219.20
BH13	0-4	30	7	18.70	15.70	3.00	9.02	1.996	CL	A2-4	210.10
BH14	0-4	30	7	28.30	18.30	10.00	9.01	1.979	CL	A2-6	207.60
BH15	0-4	30	10	25.10	15.90	9.20	11.21	1.926	CL	A-6	204.70
BH16	0-4	30	7	22.30	14.30	8.00	10.18	1.961	CL	A2-6	229.50

4.1.4. t-test analyses

Statistical evaluation of the impact of cement, sand, and binary (sand+cement) stabilisation on the natural CBR of superficial soil was achieved through t-test analysis (Table 7). The Test results show that the difference between the variance ($V1=15.59686$) of natural/untreated CBRs and that of sand-stabilised CBRs ($V2=24.9581$) is less than 100% (i.e., $V2-V1=9.36124$). This validates the use of t-test analysis with assumed equal variance in this case (i.e., the case of natural CBR against sand-stabilised CBR). However, the difference between the variance of natural CBRs and those of cement and Binary (sand+cement) stabilised CBRs is more than 100% (i.e., their variances are twice that of the natural CBRs). This enabled the t-test analysis using assumed unequal variance.

While statistical parameters such as $\alpha=0.05$ were constant, other statistical P-values were in the order of $1.16E-05$ - $2.56E-05$, $3.93E-11$ - $7.87E-11$, and $1.06E-12$ - $2.13E-12$ under sand, cement, and Binary stabilisation, respectively. All P-values were less than 0.001 and less than the α -value (0.05), but their levels of difference from the α -value were significantly widening with response to sand, cement stabilisation, and binary stabilisation, respectively (Table 7).

4.1.5 Predictive Stabilisation Models

This paper examined three distinct machine learning methods for predicting the California Bearing Ratio (CBR). In soil stabilisation: Random Forest, XGBoost, and Explainable Boosting Machine (EBM). Each of the models possesses unique advantages, and their appropriateness differs according to accuracy, interpretability, and computational efficiency (Table 8).

5. Discussion

5.1 Compaction and classification behaviour of soils under natural conditions

The suitability of superficial soils for road pavement construction depends on their classification and compaction characteristics (Avwenagha et al. 2014b; Tse and Ogunyemi 2016; Avwenagha et al. 2024). The general dominance of sand over fines in almost the entire sample locations (specifically BH2-16), with an average of 73.13% sand content and less than 35% fines) confirms the soils are mainly granular soils of excellent subgrade quality based on the AASHTO classification scheme. However, the reverse dominance of 96.5% fines over sand in BH1 implies the minor presence of clayey soil material with poor subgrade quality. The granular soils with liquid limit (LL) values (<33.0 , Table 3) and Plasticity index (PI) ($<12.40\%$) are further classified as A-3, A2-4, 2-6 and 2-7 while the clayey/silty- clayey soils with LL (33.69.0%) and PI (13.6-22%) are grouped as A-4, A-6 and A7-5.

Moreover, the range of the Optimum Moisture Content (OMC) of the soils (8.41-23.0%) indicates that the superficial soils are sands and clayey/silty soils (Arora 2003), and the average of OMC (9.91%) implies a general dominance of sands (Arora 2003). This further corroborates the granular and silty/clayey soil classification by the AASHTO scheme.

A shift in the soil classification from A-7, A-6, A-4 to A-2 and OMC from 23.0-8.41% shows a gradual increase in soil consistency, which has resulted in the CBR range from 3-17.90% under natural/ plain conditions of compaction (Table 3 and Figure 4). This range of CBR demonstrates that the soils are competent subgrade but incompetent subbase and base courses for road construction, as their CBRs are less than 30% and 80% respectively (Nigeria 1997).

Table 7: Geotechnical impact Assessment of sand, cement, and binary stabilisation using two-sample t-test assuming equal/unequal variance.

S/N	CBR of Natural soils (%)	Sand Stabilisation		Cement Stabilisation		Binary Stabilisation	
		CBR (%)	t- Test Results (equal variance)	CBR (%)	t- Test Results (unequal variance)	CBR (%)	t- Test Results (unequal variance)
1	16.20	28.80	Variance (V_1) 15.59686	171.7	Variance (V_1) 15.59686	130.7	Variance ($V1$) 15.59686
2	11.90	19.10	Variance (V_2) 24.9581 t-stat: -5.06401 P(T<=t) (one tail: 1.16E-05) $\alpha:0.05$ Df = 28 tcritical (one tail): 1.701131 P(T<=t) (two tail: 2.56E-05) tcritical (two tail): 2.048407	193.3	Variance (V_3) 1006.822	227.00	Variance ($V4$) 1141.507
3	10.10	18.70		128.5	207.40	207.40	207.40
4	15.90	18.70		170.0	221.70	221.70	221.70
5	15.00	24.10		168.7	t-stat: -17.2562	214.60	t-stat: -22.53
6	15.50	26.70		163.4	P(T<=t) (one tail: 3.93E-11)	229.90	P(T<=t) (one tail: 1.06E-12)
7	17.90	27.50		168.0	$\alpha:0.05$	198.80	$\alpha:0.05$
8	17.80	25.70		189.2	Df = 14	215.20	Df = 14
9	17.30	26.20		175.6	tcritical (one tail): 1.76131 P(T<=t) (two tail: 7.87E-11) tcritical (two tail): 2.144787	215.10	tcritical (one tail): 1.76131 P(T<=t) (two tail: 2.13E-12) tcritical (two tail): 2.144787
10	16.20	26.70		130.0		272.50	
11	15.80	26.20		150.3		107.00	
12	17.30	28.60		143.3		219.20	
13	14.10	20.40		178.9		210.10	
14	10.60	17.00		133.6		207.60	
15	13.70	20.40		185.0		204.70	
16	3.00	11.00		71.30		229.50	

A two-sample t-test assuming equal/unequal variance

Table 8: Model comparison table.

Criteria	Random Forest	XGBoost	EBM (Explainable Boosting Machine) Model
R² Score	0.46	.51	0.44
Mean Squared Error	46.5	42.3	48.0
Interpretability	Moderate	Low	High
Speed (Training Time)	Fast	Moderate-Fast	Moderate-Slow
Hyperparameter Tuning	Minimal	Required	Minimal
Best Use Case	General robustness	High accuracy tasks	Stakeholder transparency
Feature Insights	Ranked importance	Ranked importance	Visual additive feature plots

This pavement deficiency of superficial soils in a deltaic environment has been noticed by many researchers (Omotosho and Eze-uzomaka 2008; Avwenagha et al. 2014a; Imafidon et al. 2021; Etim et al. 2022; Avwenagha et al. 2024). Hence, there is a need for soil stabilisation to improve the engineering performance, consistency, and soil waterproofing effect of soils (Amu and Adetuberu 2010).

5.1.1 Impact of sand stabilisation

In response to sand stabilisation using 30wt% sand, there was an improvement in the natural soil grade, resulting in

a decrease in liquid limit, plastic limit, and Plasticity indices of the natural soils (Figure 6). The impact of the stabilisation on soil grade is that natural soils, which were predominantly of A2-4, A2-6, A-6, and A7-5 characteristics, were upgraded to A2-4, and A2-6. This translated to an increase in CBR from a natural range of 3-17.9% to 11-28.80% (Table 4, Figures 4 and 5A). The low-highly plastic, clayey/silty soil materials, which were dominantly of A7-5, and A-6 characteristics, were upgraded to low plasticity clays of A2-6 and A2-4 characteristics, which resulted in elevated CBR of 9.5-28.3% (Table 4, Figures 5A and 7). The elevated CBR range did not exceed the 30% Nigeria 1997 standard,

which shows the soils have improved in subgrade quality but remain incompetent sub-base and base-course materials for road construction (Nigeria 1997). This implies that sand stabilisation mainly improves the subgrade quality of deltaic soils, not their performance to subbase quality (Omotosho and Eze-uzomaka 2008; Avwenagha 2021). This is because it significantly affects AASHTO soil grade but has a negligible impact on the inter-particle bonding of soils.

5.1.2 Cement stabilisation

The technical and economic viability of cement stabilisation is determined by the AASHTO soil grade of the natural soil based on BS12 (BSI 1990). Hence, the granular soil grades (A2-4, A-3, A2-6) were stabilised with 7wt% cement, while the clayey/silty soil grades (A-6 and A7-5) were stabilised with 10% and 11wt% cement, respectively (Table 5). Upon cement stabilisation, the natural CBR of low-highly plastic silty/clayey soils (A-6 and A7-5) increased from a range of 3-10.60% to 71.3-128% at 10-11wt% cement. The stabilisation also increased the natural CBR of the granular soils from the range of 11.90%-17.90% to 130.30-193% at 7wt% cement. The low-fines presence in granular soils reduces water demand and water-to-cement ratio in cement hydration (to form Calcium-Silicate-Hydrate gel), which enhances soil particle bonding to produce a denser and more impermeable soil (Wei and Ku 2020; Xiu et al. 2021). The relatively high CBR response of granular soil to cement stabilisation confirms that the effectiveness of cement stabilisation increases with decreasing soil cohesion and fines content. This stabilisation favours granular soils and validates similar works (Aiban 1994; Pillappa 2005; Venkatarama et al. 2012; Puppala et al. 2015; Wei and Ku 2020; Xiu et al. 2021).

Except for BH2, BH9, and BH16 with CBR above 180% at 7wt% cement, other soils with lower CBR values (below 180%) under cement-stabilised condition, have been upgraded from their subgrade to a sub-base status, but remain incompetent base-course materials as their CBR is less than 180% under cement-stabilised conditions (Nigeria 1997, Figure 7). Contrary to other works (Omotosho and Eze-uzomaka 2008), samples of BH2, BH9, and BH16 show that cement-stabilisation of deltaic laterites to base quality (i.e, above 180% CBR) could be viable at 7wt% cement. Further cement stabilisation beyond 7wt% cement would be economically unviable (Nigeria 1997).

5.1.3 Binary (sand+cement) stabilisation

With the intent of producing base-quality soils as well as enhancing cement economy using cheap and readily available materials like sand, the binary stabilisation was engaged. Due to the impact of binary stabilisation, the naturally fines-dominated soil of BH1 was upgraded to granular soils (precisely, A2-4) by the addition of 30wt% sand (for samples BH2-15) and 55wt% sand (for BH1) at a uniform 7 wt. % of cement. General addition of 7wt% cement improved the natural CBR range of 3-17.90% to 110-229.50% with average values of 212% (Table 5, Figure 5C). Effective cement stabilisation is also enabled by cementitious hydration reaction (that is, cement-soil-water reaction), which

is favoured by relatively high sand content over fines (Roshan et al. 2022; Amadi et al. 2025). The CBR results show that binary stabilisation predominantly reduces cohesion by sand addition, thereby improving the AASHTO soil grade for effective cement stabilisation. Superficial soils of the area responded most positively to binary stabilisation, resulting in higher CBR values. The CBR values (198-80.272.50%) indicate that the soils are compliant with base quality, except for the sub-base quality produced at BH1 and BH11, which have CBR values of 130.7% and 107%, respectively (see Table 6). This exception arises from a low cement-to-sand ratio with the addition of 55 wt% sand to soil from BH1 and 30 wt% sand to cohesionless (A-3) soil from BH11. The ratio effect weakened the cementation of the soils, resulting in a low CBR. All the explored stabilisation schemes have not only impacted the CBR of the soils but have also impacted the geometry and position of the compaction curves of representative soil samples (Figure 8).

5.1.4 Geotechnical impact assessment of soil stabilisation using Two-Sample T-Test assuming equal variance

From a t-test perspective, the fall of P-values below 0.001 implies that the stabilisation schemes had a strong impact on the CBR of the natural soils. Moreover, the sequential fall in P-values below α implies a significantly increasing impact of sand, cement, and Binary (sand + cement) stabilisation on the natural soils. The order of impact confirms that binary (sand + cement) stabilisation is the most technically viable scheme of them all. The Test means that the increasing impact is not by chance but by some obvious reasons. From the geotechnical point of view, the variation in impact is due to a gradual improvement in AASHTO soil grade and inter-particle bonding of the untreated soils under the influence of the various stabilisation schemes (with progress from sand through cement to binary stabilisation). This further validates the low, medium-high, and high CBRs recorded by the soils in response to these stabilisation schemes (Tables 3 to 6).

5.1.5 Performance evaluation of statistical models

The Random Forest served as the preliminary baseline model. It exhibited mediocre performance with an R^2 score of roughly 0.46 and a mean squared error (MSE) of about 46.5. Random Forest models exhibit resilience to overfitting and yield satisfactory findings with minimal modification, rendering them appropriate for exploratory research.

XGBoost (Extreme Gradient Boosting) was subsequently utilised on the identical dataset. It surpassed Random Forest in both accuracy and error minimisation, attaining a superior R^2 score (0.51) and reduced MSE (42.3). XGBoost is recognised for its capacity to model intricate, nonlinear connections and frequently produces superior outcomes in tabular data contexts.

EBM (Explainable Boosting Machine), implemented here, merits attention. EBM offers an interpretable model framework akin to Generalised Additive Models (GAMs), enhanced by the application of boosting. It would enable engineers and domain specialists to visualise the exact impact of each feature on the CBR prediction. Although marginally less precise than XGBoost, its transparency renders it suitable for critical decision-making.

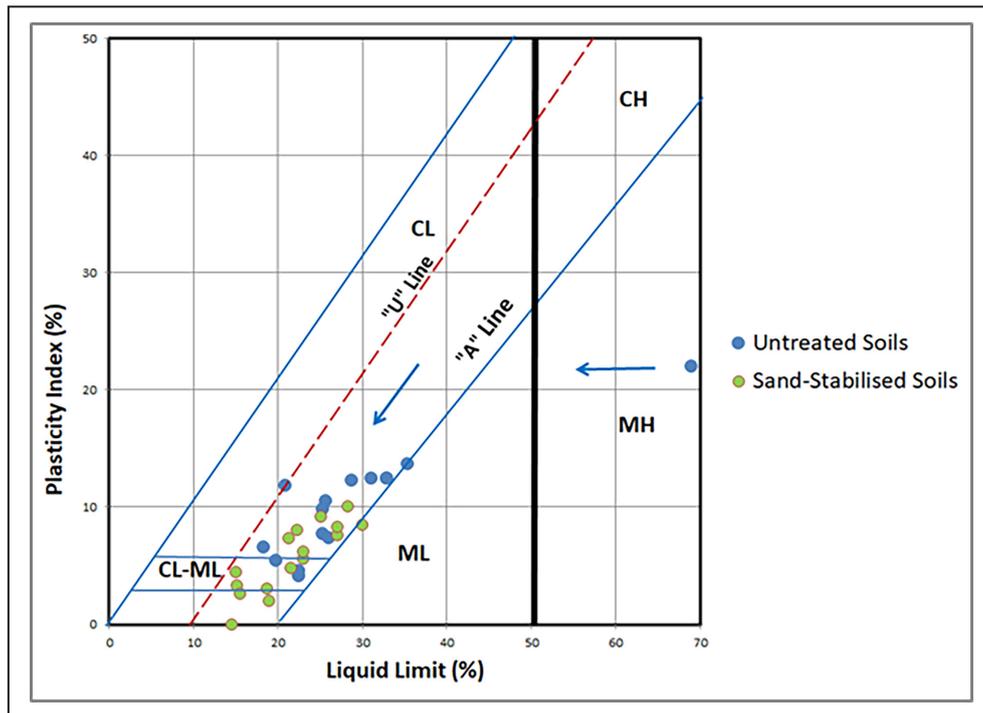


Figure 6: Impact of sand Stabilisation on soil consistency limits. Note that the natural soils (blue dots) initially were distributed across the medium-low (ML) to medium-high (MH) plasticity silt zones. Upon sand-stabilisation, the sample points (as indicated by blue arrows) drifted towards the left, away from the ML-MH zone, and downwards along the low-plasticity soil zone (as indicated by the blue arrows). This implies that sand stabilisation decreases the plasticity index and liquid limits of soils and consequently increases soil consistency (strength/stiffness).

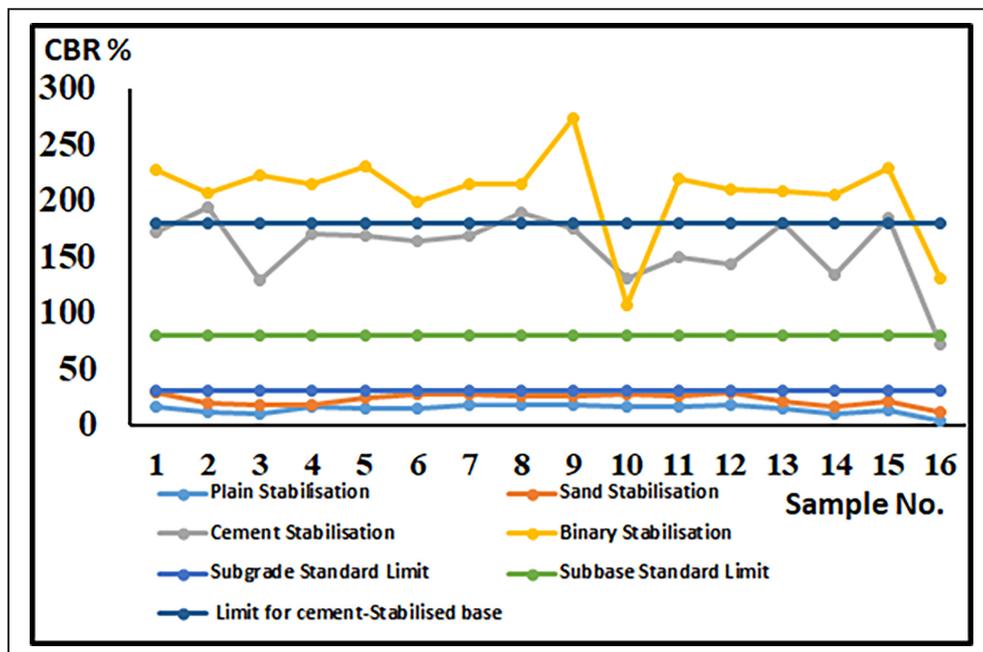


Figure 7: CBR response to sand, cement, and binary stabilisation. Note that the parallel lines (coloured with blue, green, and dark blue) are standard limits (Nigeria 1997) that define subgrade, subbase, and base-quality soils in road pavement designs. The wavy lines indicate the magnitude of CBR recorded at various sample locations (No.1-16) under plain/natural, sand, cement, and binary-stabilised conditions. CBR responses under plain and sand stabilisation were within the subgrade quality limit (blue line at 30% CBR). The response partly exceeded the Cement-stabilised base limit (Dark blue line at 180% CBR) during cement stabilisation, while over 95% of the responses exceeded the base limit under conditions of Binary (Cement + sand) stabilisation. The increasing CBR trend shows that all the stabilisation schemes increase soil density, reduce void ratio, and the Water Holding Capacity (WHC). While soil-cement matrix interaction increases inter-particle bonding during cement stabilisation, Binary (Cement + sand) stabilisation increases both inter-particle bonding and soil grade, which are the prevailing factors of Stabilisation. Hence, the Highest CBR response from binary stabilisation.

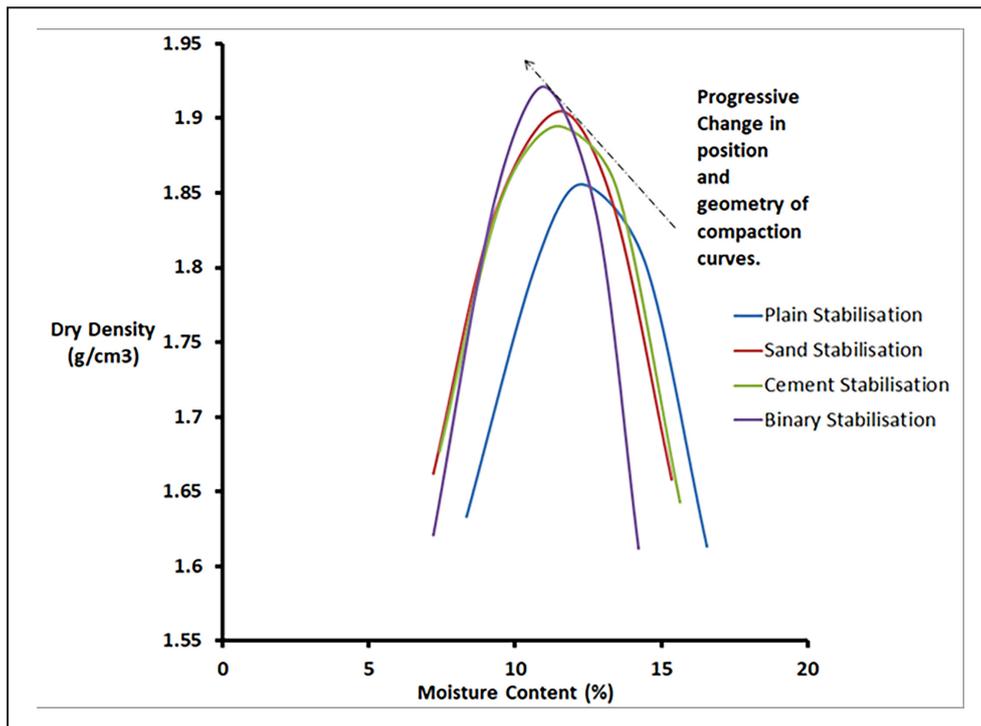


Figure 8: Graphical impact of plain, sand, cement, and binary stabilisation. Note that with response to plain, sand cement, and binary stabilisation, there is a shift in the compaction curves from right to left while the steepness of the curves increases. The leftward shift and increasing steepness imply decreasing OMC and increasing MDD/soil grading, respectively. These changes ultimately translated to increasing CBR.

6. Conclusions

The Geotechnical stabilisation and prediction modelling of superficial soils in Warri under the influence of sand, cement, and binary stabilisers has resulted in the following findings:

Granular soils of A-2 and A-3 signatures are the dominant natural characteristics of the deltaic laterites.

Untreated stabilisation of the deltaic laterites does not exceed subgrade quality.

Sand stabilisation greatly affects the AASHTO soil grade, but has a slight impact on the CBR performance of the deltaic soils

Subbase-quality stabilisation of deltaic soils could be both technically and economically viable at 7wt% cement.

Subbase-quality and base course-quality stabilisation are viable under cement and binary stabilisation, respectively.

Binary (sand+cement) stabilisation is the most viable solution to pavement deficiency from the geotechnical and t-test perspectives.

Extreme Gradient Boosting (XG boost) machine learning model is a more viable option than the Random Forest Model (RFM) and Extreme Boosting Machine (EBM) model in CBR prediction of treated superficial soils.

Acknowledgements

The authors benefited from the invaluable supervision and mentorship of Professor Christopher N. Akujieze, from the Department of Geology at the University of Benin, Nigeria. Regards to Dr S.A. Salami, Department of Geology, University of Benin, and Mr Timothy Serun, Senior laboratory technician, at Levante Quality Control Laboratory, for their sound inputs to the completion of this work.

Authorship credits

Author	A	B	C	D	E	F
EOA						
JO						
BO						
OO						
SOE						
OME						
GOA						

A - Study design/ Conceptualization B - Investigation/ Data acquisition
 C - Data Interpretation/ Validation D - Writing
 E - Review/Editing F - Supervision/Project administration

Editor’s acknowledgement

The Editor acknowledges the effort of JGSB’s anonymous reviewers.

References

Adejuwon O.A. 2012. Rainfall Seasonality in the Niger Delta Belt, Nigeria. *Journal of Geography and Regional Planning*, 5(2), 51-60. <https://doi.org/10.5897/JGRP11.096>

Aiban S.A. 1994. A study of sand stabilisation in eastern Saudi Arabia. *Engineering Geology*, 38(1-2), 65-79. [https://doi.org/10.1016/0013-7952\(94\)90025-6](https://doi.org/10.1016/0013-7952(94)90025-6)

Akpokodje E.G. 1987a. The engineering geological characteristics and classification of the major superficial soils of the Niger Delta. *Engineering Geology*, 23(3-4), 193-211. [https://doi.org/10.1016/0013-7952\(87\)90090-1](https://doi.org/10.1016/0013-7952(87)90090-1)

Akpokodje E.G. 1987b. The engineering geology of Niger Delta. In: *Conference Soil Mechanics and Foundation Engineering*, 9, 751-760.

Amadi A.A., Kolo S.S., Yusuf A., Eze F.E., Salihu U. 2025. Stabilisation characteristics of cemented lateritic soil produced with selected

- cement types. *Cement*, 19, 100136. <https://doi.org/10.1016/j.cement.2025.100136>
- Amu O.O., Adetuberu A.A. 2010. Characteristics of bamboo leaf ash stabilisation on lateritic soils in highway construction. *International Journal of Engineering and Technology*, 2(4), 212-419.
- Arora K.A. 2003. *Soil mechanics and foundation engineering*. New Delhi, Standard Publ., 886 p.
- Arumala J.O., Akpokodje E.G. 1987. Soil properties and pavement performance in the Niger Delta. *Quarterly Journal of Engineering Geology and Hydrogeology*, 20 (4), 287-296. <https://doi.org/10.1144/GSL.QJEG.1987.020.04.05>
- Avwenagha E.O. 2021. Geophysical, mineralogical and geotechnical investigations of soils underlying some buildings in Warri, southern Nigeria. PhD thesis, University of Benin, Benin City.
- Avwenagha E.O., Akpokodje E.G., Tse A.C. 2014a. Geotechnical properties of subsurface soils in Warri, Western Niger Delta. *Journal of Earth Sciences and Geotechnical Engineering*, 4(1), 89-102.
- Avwenagha E.O., Arong T.O., Overare B., Okunuwadje S.E., Osokpor J. 2014b. Classification and compaction characteristics of lateritic soils of Warri, Delta State, Nigeria. *Advances in Applied Science Research*, 5(3), 451-457.
- Avwenagha E.O., Overare B., Osokpor J., Itiowe K., Aigbadon G.O. 2024. Modelling on earthwork feasibility analyses of geotechnical and georesistivity fingerprints of subsoils: Application to tank farm, road, and building developments in part of the Niger Delta. *Modelling Earth Systems and Environment*, 10, 4939-4956. <https://doi.org/10.1007/s40808-024-02043-x>
- Bayon G., Garzanti E., Dinis P., Beaufort D., Barrat J.A., Germain Y., Trinquier A., Barbarano M., Overare B., Adeaga O., Braquet N. 2024. Contribution of Saharan dust to chemical weathering fluxes and associated phosphate release in West Africa. *Earth and Planetary Science Letters*, 641, 118845. <https://doi.org/10.1016/j.epsl.2024.118845>
- BSI. 1990. BS 1377-1557: methods for tests for soils for civil engineering purposes. London, British Standard Institute.
- BSI. 2015. BS 5930: code of practice for site investigation. London, British Standard Institute.
- BSI. 1990. BS12: specification for Portland cement. London, British Standard Institute.
- BSI. 2022. BS 1377-2: methods of test for soil for civil engineering purposes - Part 2: classification test. London, British Standard Institute.
- BSI. 2022. BS 1377-4: methods of test for soil for civil engineering purposes- Part 4: compaction related tests. London, British Standard Institute.
- BSI. 2022. BS 1377-9: methods of test for soil for civil engineering purposes - Part 9: in-situ tests. London, British Standard Institute.
- BSI. 1990. BS 1924: method of test for stabilized soils. London, British Standard Institute.
- Casagrande A. 1948. Classification and Identification of Soils. *Transaction, ASCE*, 113, 901-991.
- Doust H., Omatsola E. 1990. Niger Delta. In: Edwards J.D., Santogrossi P.A. (eds.) *Divergent/passive margin basins*. American Association of Petroleum Geologists, 48, 239-248. <https://doi.org/10.1306/M48508C4>
- Etim R.K., Ekpo D.U., Udofia G.E., Christopher I. 2022. Evaluation of lateritic soils stabilised with lime and periwinkle shell ash (PSA) admixture bound for sustainable road materials. *Innovative Infrastructure Solution*, 7(62), 1-17. <https://doi.org/10.1007/s41062-021-00665-z>
- Goodarzi A.R., Goodarzi S., Akbari H.R. 2015. Assessing geo-mechanical and micro-structural performance of modified expansive clayey soil by silica fume as industrial waste. *IJST –Transactions of Civil Engineering*, 39(C2), 333–350. <https://doi.org/10.22099/IJSTC.2015.3138>
- Imafidon D., Ogirigbo O.R., Ehiorobe J.O. 2021. Improvement of deltaic lateritic soils using river sands and cements for use as pavement construction material. *Nigerian Journal of Technology*, 40(2), 168-176. <https://doi.org/10.4314/njt.v40i2.1>
- Jain A.K., Jha A.K., Shivanshi. 2020. Geotechnical behaviour and micro-analyses of expansive soil amended with marble dust. *Soils and Foundations*, 60(4), 737-757. <https://doi.org/10.1016/j.sandf.2020.02.013>
- Latifi N., Horpibulsuk S., Meehan C.L., Abd Majid M.Z., Rashid A.S.A. 2016. Xanthan gum biopolymer: an eco-friendly additive for stabilisation of tropical organic peat. *Environmental Earth Sciences*, 75(9), 825. <https://doi.org/10.1007/s12665-016-5643-0>
- Latifi N., Rashid A.S.A., Siddiqua S., Horpibulsuk S. 2015. Micro structural analysis of strength development in low- and high swelling clays stabilized with magnesium chloride solution – A green soil stabilizer. *Applied Clay Science*, 118, 195–206. <https://doi.org/10.1016/j.clay.2015.10.001>
- Mishra S., Sachdeva S.N., Manocha R. 2019. Subgrade soil stabilisation using stone dust and coarse aggregate: a cost-effective approach. *International Journal of Geosynthetics and Ground Engineering*, 5(20). <https://doi.org/10.1007/s40891-019-0171-0>
- Mogborukor J.O., Arisabor L., Okoh E. 2021. Population growth and its effect on family standard of living in Warri metropolis, Nigeria. *European Modern Studies Journal*, 5(5), 17-29.
- MoRTH. 2013. Specifications for road and bridge work. New Delhi, Indian Roads Congress.
- Nigeria. 1997. General specifications (roads and bridges): volume II. Abuja, Federal Ministry of Works and Housing, 119 p.
- Offodile M.E. 1991. An approach to groundwater study and development in Nigeria. Jos, Nigeria, Mecon Services Ltd, 245 p.
- Ogbe O.B., Okoro A.U., Ogarue D.O., Osokpor J., Overare B., Ocheli A., Opatola A.O., Oluwajana O.A. 2021. Reservoir hydrocarbon prospectivity and productivity evaluations of sands S-600 and S-700 of Fega field, onshore Niger Delta Basin, Nigeria. *Journal of African Earth Sciences*, 184, 104311. <https://doi.org/10.1016/j.jafrearsci.2021.104311>
- Okagbue C.O. 1989. Geotechnical and environmental problems of the Niger Delta. *Bulletin of the International Association of Engineering Geology*, 40(1), 119-126. <https://doi.org/10.1007/BF02590349>
- Okagbue C.O., Onyeobi T.U.S. 1999. Potential of marble dust to stabilize red tropical soils for road construction. *Engineering Geology*, 53(3-4), 371-380. [https://doi.org/10.1016/S0013-7952\(99\)00036-8](https://doi.org/10.1016/S0013-7952(99)00036-8)
- Olobaniyi S.B., Owoyemi F.B. 2006. Characterization by factor analysis of chemical facies of groundwater in the Deltaic Plain Sands aquifer of Warri, western Niger Delta, Nigeria. *African Journal of Science and Technology*, 7(1), 73-81. <https://doi.org/10.4314/ajst.v7i1.55201>
- Omotosho O., Eze-Uzomaka O.J. 2008. Optimal stabilisation of deltaic laterite. *Journal of the South African Institution of Civil Engineering*, 50(2), 10-17. Available online at: <https://scielo.org.za/pdf/jsaice/v50n2/02.pdf> / (accessed on 12 January 2026).
- Osokpor J., Lucas F.A., Osokpor O.J., Overare B., Alaminioakuma G.I., Ogbe O.B., Daniya T.S., Avwenagha E.O. 2016. Petroleum potential of Paleogene-Neogene age sediments in well TN-1, western Niger Delta basin. *Pacific Journal of Science and Technology*, 17(1), 288–300. <https://doi.org/10.13140/RG.2.2.23251.68649>
- Osokpor J., Lucas F.A., Osokpor O.J., Overare B., Izeze O.E., Avwenagha E.O. 2015. Palynozonation and lithofacies cycles of Paleogene to Neogene age sediments in PML-1 well, northern Niger Delta Basin. *Pacific Journal of Science and Technology*, 16(2), 286-297. <https://doi.org/10.13140/RG.2.2.20210.81606>
- Osokpor J., Overare B. 2019. Source rock evaluation and hydrocarbon potentials in the northern Depobelt, Niger Delta Basin. *Journal of Mining and Geology*, 55(1), 17-28.
- Overare B., Avwenagha E.O., Okpara E., Osokpor J., Ogbe O.B., Overare A.E., Ogueh E.D. 2016. Hydro-geochemical attributes of Quaternary Sands in Warri, western Niger Delta, Nigeria. *Pacific Journal of Science and Technology*, 17(1), 301-310. <https://doi.org/10.13140/RG.2.2.16855.37281>
- Overare B., Azmy K., Garzanti E., Avwenagha E.O., Emudianughe E.O. 2024. Diagenetic imprints in the reservoirs of Agbada Formation, Niger Delta Basin: Implication for reservoir quality and appraisal of calcite cement. *Marine and Petroleum Geology*, 63, 106746. <https://doi.org/10.1016/j.marpetgeo.2024.106746>
- Overare B., Azmy K., Garzanti E., Osokpor J., Ogbe O.B., Avwenagha E.O. 2021. Decrypting geochemical signatures in subsurface Niger delta sediments: Implication for provenance, weathering, and paleoenvironmental conditions. *Marine and Petroleum Geology*, 126, 104879. <https://doi.org/10.1016/j.marpetgeo.2020.104879>
- Pastore G., Garzanti E., Vermeesch P., Bayon G., Resentini A., Braquet N., Overare B. 2023. The zircon story of the Niger River: Time-structure maps of the West African Craton and discontinuous propagation of provenance signals across a disconnected sediment-routing system. *JGR Earth Surface*, 128(11), e2023JF007342. <https://doi.org/10.1029/2023JF007342>
- Pillappa G. 2005. Field and experimental studies to assess the performance of stabilisedec expansive clay. MSc Dissertation, University of Texas, Arlington. Available online at: https://mavmatrix.uta.edu/civilengineering_theses/13/ / (accessed on 12 January 2026).
- Puppala A.J., Pedarla A., Bheemasetti T. 2015. Chapter 10 - Soil modification by admixtures: concepts and field applications.

- In: Indraratna B., Chu J., Rujikiatkamjorn C. (eds). Ground improvement case histories: chemical, electrokinetic, thermal, and bioengineering. Butterworth-Heinemann, p. 291-309. <https://doi.org/10.1016/B978-0-08-100191-2.00010-1>
- Reijers T.J.A. 2011. Stratigraphy and sedimentology of the Niger Delta. *Geologos*, 17(3), 133-162. <https://doi.org/10.2478/v10118-011-0008-3>
- Roshan M.J., Rashid A.S.B.A., Hezmi M.A.B., Nejabi M.N., Josuh S.N., Razali R. 2022. Evaluation of cement-stabilised residual soil on macro-and micro-scale for road construction. *Journal of Engineering and Applied Science*, 69(1), 109. <https://doi.org/10.1186/s44147-022-00165-6>
- Sajini F.I. 2021. Human population growth and the socioeconomic effects in Warri metropolitan city, Delta State. *Linguistics and Culture Review*, 5(S1), 878-889. <https://doi.org/10.21744/lingcure.v5nS1.1472>
- Sathyapriya S., Arumairaj P.D. 2016. Microfabric and mineralogical studies on the stabilisation of expansive soil using cement industry wastes. *Indian Journal Geo-Marine Sciences*, 45(6), 807-815
- Short K.C., Stauble A.J. 1967. Outline of the Geology of the Niger Delta. *American Association Petroleum Geology Bull*, 51(5), 761-779.
- Tse A.C., Ogunyemi A. 2016. Geotechnical and chemical evaluation of tropical soils in deltaic environment: implications for road construction. *Journal of Geography and Geology*, 8(3), 42-51. <https://doi.org/10.5539/jgg.v8n3p42>
- Ugbe F.C. 2011. Basic engineering geological properties of lateritic soils from western Niger Delta. *Research Journal of Environmental and Earth Sciences*, 3(5), 571-577.
- Ugbe F.C., Odibo O.F., Emioge E.A., Etobro A.A.I., Nwakaji K.N. 2022. Mineralogical and geotechnical properties of subgrade soils along failed portions of Abavo-Urhonigbe road, western Niger Delta Nigeria. *Journal of Applied Sciences and Environmental Management*, 26(12), 1970-1976. <https://doi.org/10.4314/jasem.v26i12.11>
- Ugwu I.J., Okobiebi O.O., Overare B., Ogbiede S.E. 2023. 3D static reservoir modelling: a case study of the Izu Field, coastal swamp depobelt, Niger Delta Basin. *Arabian Journal of Geosciences*, 16, 42. <https://doi.org/10.1007/s12517-022-11114-1>
- Venkatarama R.B.V. 2012. 13 - Stabilised soil blocks for structural masonry in earth construction. In: Hall M.R., Lindsay R., Krayenhoff M. (eds). *Modern earth buildings: materials, engineering, constructions and applications*. Woodhead Publishing, p. 324-363. <https://doi.org/10.1533/9780857096166.3.324>
- Wei X., Ku T. 2020. New design chart for geotechnical ground improvement: characterising cement-stabilised sand. *Acta Geotechnica*, 15, 999-1011. <https://doi.org/10.1007/s11440-019-00838-2>
- Xiu Z., Wang S., Ji Y., Wang F., Ren F., Nguyen V. 2021. The effects of dry and wet rock surfaces on shear behavior of the interface between rock and cemented paste backfill. *Powder Technology*, 381, 324-337. <https://doi.org/10.1016/j.powtec.2020.11.053>